Prediction of the ferroelectric ground state of graphene and other two-dimensional crystals

S. A. Mikhailov*
Institute of Physics, University of Augsburg, D-86135 Augsburg, Germany

(Dated: March 20, 2013)

A spontaneous electric polarization in the many-body ground state of graphene and other similar materials, such as boron nitride and bilayer graphene, is predicted. This transition to the ferroelectric ground state is a consequence of strong Coulomb interaction between π-electrons in two-dimensional lattices.

arXiv:1303.3928v1 [cond-mat.mes-hall] 15 Mar 2013

Graphene, the first truly two-dimensional (2D) material [1–3], consists of a monolayer of carbon atoms arranged in a hexagonal lattice, Fig. 1, for a review see [4]. Each carbon atom has four electrons on its outer shell. Three of them (σ-electrons) are strongly bound to the neighboring atoms and thus form the lattice. The forth electrons of each atom (π-electrons) are relatively weakly bound to their hosts and can move through the whole lattice. Their motion can be described by the many-body Hamiltonian

$$\hat{H} = \sum_{i=1}^{N} \left(\frac{\hat{\boldsymbol{p}}_i^2}{2m} + U(\boldsymbol{r}_i) \right) + \frac{1}{2} \sum_{i \neq j}^{N} \frac{e^2}{|\boldsymbol{r}_i - \boldsymbol{r}_j|} \qquad (1)$$

where

$$U(\boldsymbol{r}) = \sum_{j=1}^{N} U_a(\boldsymbol{r} - \boldsymbol{R}_j) \qquad (2)$$

is the periodic potential of the lattice, $U_a(\boldsymbol{r})$ is the atomic potential and $\boldsymbol{R}_j$ are the coordinates of the atoms. In the intrinsic material (which we will consider here) the number of π-electrons N equals the number of atoms.

The Schrödinger problem with the Hamiltonian (1) is usually solved neglecting electron-electron interaction. Omitting the Coulomb term in (1) one reduces the many-body problem to the single-particle one for an electron in the periodic potential (2) of the hexagonal lattice. The latter problem is solved within the tight-binding approximation [5] which results in the single-particle electron spectrum shown in Fig. 2. The electron-electron interaction is then taken into account only by assuming that all states of the lower energy band are occupied and all states of the upper band are empty. The many-body ground state wave function in this approach has thus the form of a single Slater determinant composed of the single-particle tight-binding orbitals. This ground state is non-degenerate. Similarly one treats the problem of bilayer graphene or of the two-atomic monolayer hexagonal lattice (e.g. boron nitride).

The goal of this Letter is to show that this commonly used approach is not completely valid. Consider two sorts of atoms, A and B, with the static atomic polarizabilities α_A and α_B. Being isolated and placed in an external static electric field $\boldsymbol{E}_0$, they acquire dipole moments $\boldsymbol{d}_A = \alpha_A \boldsymbol{E}_0$ and $\boldsymbol{d}_B = \alpha_B \boldsymbol{E}_0$, respectively. Now assume that these atoms are arranged in the plane 2D hexagonal lattice, Fig. 1, so that the atoms A occupy the sites of the triangular sublattice $\boldsymbol{A}_i = a\,(m_i \boldsymbol{\zeta}_1 + n_i \boldsymbol{\zeta}_2)$ and the atoms B – of the sublattice $\boldsymbol{B}_i = \boldsymbol{A}_i + \boldsymbol{b}$, $\boldsymbol{b} = a\boldsymbol{\xi}$, where a is the lattice constant, m_i and n_i are integer, and the vectors $\boldsymbol{\zeta}_1$, and $\boldsymbol{\zeta}_2$ and $\boldsymbol{\xi}$ are defined as follows

$$\boldsymbol{\zeta}_1 = \begin{pmatrix} 1/2 \\ \sqrt{3}/2 \\ 0 \end{pmatrix}, \ \boldsymbol{\zeta}_2 = \begin{pmatrix} -1/2 \\ \sqrt{3}/2 \\ 0 \end{pmatrix}, \ \boldsymbol{\xi} = \begin{pmatrix} 0 \\ 1/\sqrt{3} \\ 0 \end{pmatrix}. \qquad (3)$$

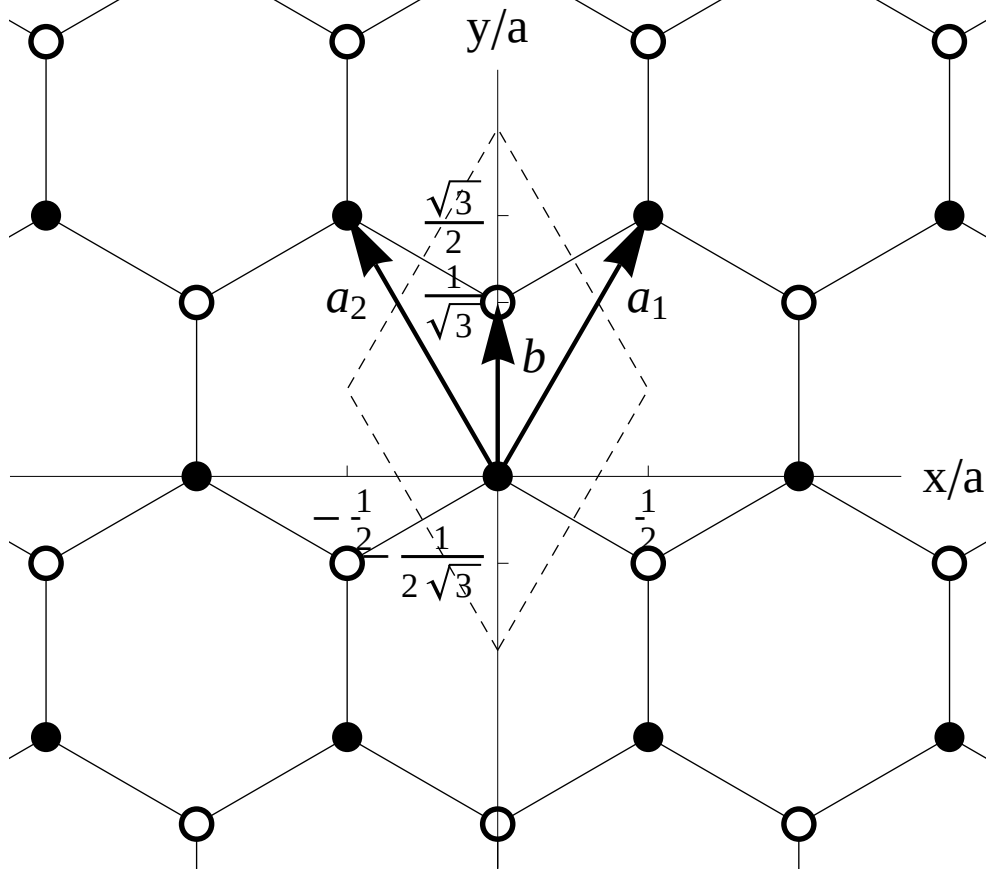

FIG. 1. The hexagonal two-dimensional lattice with two atoms per unit cell. The coordinates of the first (black circles) and second triangular sublattice (open circles) are given by the vectors $a(n_1\boldsymbol{\zeta}_1 + n_2\boldsymbol{\zeta}_2)$ and $a(n_1\boldsymbol{\zeta}_1 + n_2\boldsymbol{\zeta}_2 + \boldsymbol{\xi})$ respectively, where $\boldsymbol{\zeta}_1$, $\boldsymbol{\zeta}_2$, and $\boldsymbol{\xi}$ are defined in (3) and a is the lattice constant.

Consider the response of such a lattice to the external electric field $\boldsymbol{E}_0$ *parallel* to the layer. Under the action of this field each atom gets polarized but in the lattice one should take into account that the *local* field acting on the atom at the given point differs from the external one by the field produced by all other dipoles at this point [6]:

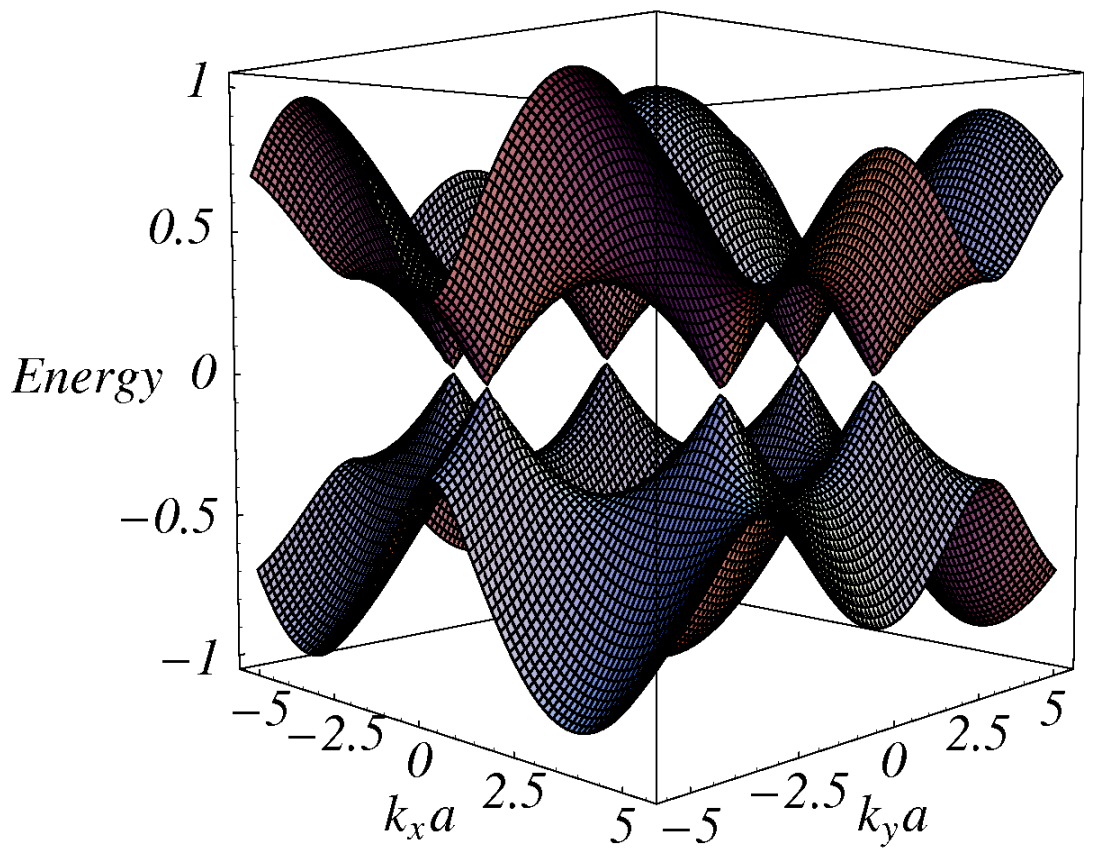

FIG. 2. The tight-binding spectrum of electrons in a two-dimensional hexagonal lattice of Fig. 1 with identical atoms in both sublattices.

$$\boldsymbol{d}_i^A = \alpha_A \boldsymbol{E}_{loc}(\boldsymbol{A}_i) = \alpha_A \left\{ \boldsymbol{E}_0 + \sum_{j\neq i} \frac{3(\boldsymbol{d}_j^A\cdot(\boldsymbol{A}_j-\boldsymbol{A}_i))(\boldsymbol{A}_j-\boldsymbol{A}_i) - \boldsymbol{d}_j^A|\boldsymbol{A}_j-\boldsymbol{A}_i|^2}{a^3|\boldsymbol{A}_j-\boldsymbol{A}_i|^5} + \sum_{j} \frac{3(\boldsymbol{d}_j^B\cdot(\boldsymbol{B}_j-\boldsymbol{A}_i))(\boldsymbol{B}_j-\boldsymbol{A}_i) - \boldsymbol{d}_j^B|\boldsymbol{B}_j-\boldsymbol{A}_i|^2}{a^3|\boldsymbol{B}_j-\boldsymbol{A}_i|^5} \right\}, \quad (4)$$

$$\boldsymbol{d}_i^B = \alpha_B \boldsymbol{E}_{loc}(\boldsymbol{B}_i) = \alpha_B \left\{ \boldsymbol{E}_0 + \sum_{j} \frac{3(\boldsymbol{d}_j^A\cdot(\boldsymbol{A}_j-\boldsymbol{B}_i))(\boldsymbol{A}_j-\boldsymbol{B}_i) - \boldsymbol{d}_j^A|\boldsymbol{A}_j-\boldsymbol{B}_i|^2}{a^3|\boldsymbol{A}_j-\boldsymbol{B}_i|^5} + \sum_{j\neq i} \frac{3(\boldsymbol{d}_j^B\cdot(\boldsymbol{B}_j-\boldsymbol{B}_i))(\boldsymbol{B}_j-\boldsymbol{B}_i) - \boldsymbol{d}_j^B|\boldsymbol{B}_j-\boldsymbol{B}_i|^2}{a^3|\boldsymbol{B}_j-\boldsymbol{B}_i|^5} \right\}. \quad (5)$$

Since all atoms in each sublattice are identical, i.e. $\boldsymbol{d}_i^{A,B} = \boldsymbol{d}^{A,B}$, the system of equations (4)–(5) can be written in the form:

$$d_A = \alpha_A \left\{ E_0 + \frac{d^A}{2a^3} S_{AA} + \frac{d^B}{2a^3} S_{AB} \right\}, \quad (6)$$

$$d_B = \alpha_B \left\{ E_0 + \frac{d^A}{2a^3} S_{BA} + \frac{d^B}{2a^3} S_{BB} \right\}, \quad (7)$$

where the sums $S_{AA} = S_{BB}$ correspond to the summation over the dipoles of the same sublattice,

$$S_{AA} = \sum_{j\neq 0} \frac{a^3}{|\boldsymbol{A}_j|^3} = \sum_{(m,n)\neq(0,0)} \frac{1}{(m^2+mn+n^2)^{3/2}}, \quad (8)$$

and the sums $S_{AB} = S_{BA}$ – to the dipoles of the other sublattice,

$$S_{AB} = \sum_j \frac{a^3}{|\boldsymbol{A}_j + \boldsymbol{b}|^3} = \sum_{m,n} \frac{1}{(m^2+mn+n^2+m+n+\frac{1}{3})^{3/2}}. \quad (9)$$

The series in (8) and (9) converge, and their numerical calculation gives

$$S_{AA} \approx 11.034, \qquad S_{AB} \approx 23.151. \quad (10)$$

If the atoms A and B are identical (the case of graphene) then $\alpha_A = \alpha_B = \alpha$, and Eqs. (6) and (7) give the dipole moment of each atom

$$d_A = d_B = \frac{\alpha E_0}{1 - \beta(S_{AA} + S_{AB})} \quad (11)$$

and the macroscopic polarizability of the lattice (per unit area)

$$\chi_{2D,hex} = \frac{N_s \alpha}{1 - \beta(S_{AA} + S_{AB})}. \quad (12)$$

Here $\beta = \alpha/2a^3$ and $N_s = 4/\sqrt{3}a^2$ is the surface density of atoms (the polarizability χ_{2D} of a 2D lattice has the dimensionality of length). One sees that if the lattice constant a is large, $a^3 \gg \alpha(S_{AA}+S_{AB})/2$, the correction due to the local field effects is small. It is however positive, i.e. the local field, really acting on each of the lattice atoms, is larger than the external field E_0 and points in the same direction. If a decreases, the dipole moment d and the lattice polarizability $\chi_{2D,hex}$ grows and tends to infinity when $a^3 \to \alpha(S_{AA}+S_{AB})/2$. The divergency of the polarizability $\chi_{2D,hex}$ physically means the instability of the lattice: even without the external field E_0 the lattice gets spontaneously polarized since a small fluctuation of the dipole moment of any atom leads to the polarization of the whole system in the same direction. The 2D hexagonal lattice of atoms is thus stable with respect to the spontaneous electric polarization only if

$$\frac{\alpha}{2a^3}(S_{AA}+S_{AB}) < 1. \tag{13}$$

Now we can check whether the stability condition (13) is satisfied for graphene. The lattice constant in graphene is $a = 2.46$ Å [4]. The atomic polarizability of the carbon atom is $\alpha_C \approx 1.7$ Å^3 [7]. Substituting these data in (13) we get for graphene the number,

$$\frac{\alpha_C}{2a^3}(S_{AA}+S_{AB}) \approx 1.95 > 1, \tag{14}$$

which is substantially above the stability boundary. The hexagonal graphene lattice is thus unstable with respect to the transition to a ferroelectric ground state with a finite in-plane electric polarization. The direction of the spontaneous dipole moment in the plane of the 2D lattice is arbitrary, so that the many-body ground state of graphene is degenerate, in contrast to the single-particle picture outlined above.

The same conclusion should be drawn for boron nitride and probably for many other 2D crystals. For the two-atomic hexagonal lattice Eqs. (6) – (7) give the following expressions for the dipole moments

$$d_A = \alpha_A \frac{1+\beta_B(S_{AB}-S_{AA})}{(1-\beta_A S_{AA})(1-\beta_B S_{AA}) - \beta_A\beta_B S_{AB}^2} E_0, \tag{15}$$

$$d_B = \alpha_B \frac{1+\beta_A(S_{AB}-S_{AA})}{(1-\beta_A S_{AA})(1-\beta_B S_{AA}) - \beta_A\beta_B S_{AB}^2} E_0. \tag{16}$$

The two-atomic hexagonal lattice will then be stable if the denominator in Eqs. (15)–(16) is positive. Using parameters of boron ($\alpha_B = 3.04$ Å^3) and nitrogen ($\alpha_N = 1.10$ Å^3) [7], and the lattice constant of BN, $a = 2.52$ Å, we get however a negative value of the denominator,

$$(1-\beta_B S_{AA})(1-\beta_N S_{AA}) - \beta_B\beta_N S_{AB}^2 \approx -1.78, \tag{17}$$

i.e. the BN lattice is also unstable and is in the ferroelectric ground state. One can show that the lattice of bilayer graphene is unstable, too.

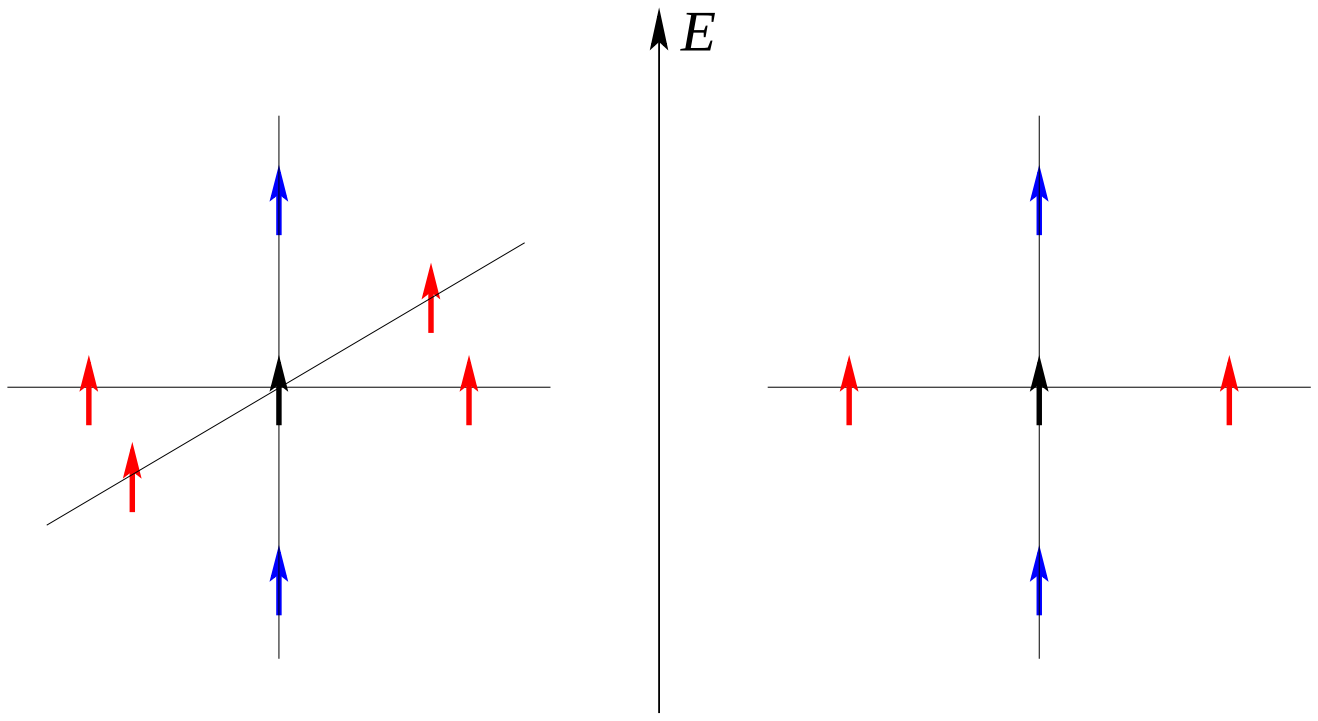

FIG. 3. The local field effects in (left) three and (right) two dimensional simple cubic/square lattice.

The much stronger tendency of 2D lattices (as compared to 3D ones) to the ferroelectric transition has a simple explanation. The increase of the local field due to dipole-dipole interaction is also the case in 3D crystals and leads to the well known Clausius-Mossotti formula for the effective macroscopic 3D polarizability [6]

$$\chi_{3D} = \frac{N_v\alpha}{1-\frac{4\pi}{3}N_v\alpha}, \tag{18}$$

where N_v is the volume density of atoms. In three dimensions, however, this effect is not so strong. This is illustrated in Fig. 3 by the example of the simple cubic/square lattices. In the 3D case, Fig. 3 (left), each dipole is surrounded by four nearest neighbors in the azimuthal direction and two neighbors in the vertical direction. Each azimuthal dipole creates the field $-\boldsymbol{d}/r^3$ opposite to the external one; the “north” and “south” dipoles produce the field $+2\boldsymbol{d}/r^3$ in the same direction as the external field. The resulting force from the nearest neighbors is thus zero. In the 2D case, Fig. 3 (right), there are only two azimuthal dipoles so that the resulting field from the nearest neighbors equals $+2\boldsymbol{d}/r^3$ and enhances the external one.

The stability condition ($\chi > 0$) is therefore typically not violated in 3D crystals. For example, for graphite parameters the denominator in (18) is positive (= 0.19). Whether any 2D (or 1D) lattice is unstable with respect to the ferroelectric transition depends on the polarizability of constituent atoms α, the lattice period a, as well as on the type of the lattice. The hexagonal lattice is unstable, as follows from (13) and (10), if

$$\frac{\alpha}{a^3} \geq 0.0585. \tag{19}$$

The similar condition for a square 2D lattice,

$$\frac{\alpha}{a^3} \geq 0.2214, \tag{20}$$

shows that it is more stable. In a linear (1D) chain of atoms a spontaneous electric polarization along the chain arises if

$$\frac{\alpha}{a^3} \geq 0.2080. \tag{21}$$

We emphasize that in all cases the system gets polarized due to the displacement of the electron density with respect to the atomic lattice which is assumed to be fixed.

The predicted ferroelectric transition is a consequence of electron-electron interaction, which is seen to be so strong in 2D lattices, that it leads to the reconstruction of the ground state (this effect could not be obtained by treating the Coulomb interaction as perturbation). The tight-binding theory of the single-particle spectrum of graphene electrons, Fig. 2, should thus be reconsidered. Notice that the spectrum of Fig. 2 was first calculated by Wallace [5] who studied the properties of three-dimensional graphite, in which the spontaneous polarization is not the case and hence the use of the tight binding theory is beyond question.

The interaction induced spontaneous electric polarization and the resulting degeneracy of the ground state of graphene and similar materials may help to better understand such effects as the minimal electric conductivity of graphene [2, 3] and the recently observed [8] spectrum reconstruction in bilayer graphene. A detailed study of all consequences from the predicted instability would be very interesting and will be done in future publications.

The author gratefully acknowledges support of this work from the Deutsche Forschungsgemeinschaft.

---

* Electronic mail: sergey.mikhailov@physik.uni-augsburg.de

[1] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov, Science **306**, 666 (2004).

[2] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, M. I. Katsnelson, I. V. Grigorieva, S. V. Dubonos, and A. A. Firsov, Nature **438**, 197 (2005).

[3] Y. Zhang, Y.-W. Tan, H. L. Stormer, and P. Kim, Nature **438**, 201 (2005).

[4] A. H. Castro Neto, F. Guinea, N. M. R. Peres, K. S. Novoselov, and A. K. Geim, Rev. Mod. Phys. **81**, 109 (2009).

[5] P. R. Wallace, Phys. Rev. **71**, 622 (1947).

[6] C. Kittel, *Introduction to Solid State Physics* (Wiley, Hoboken, NJ, 2005), 8th ed.

[7] P. Schwerdtfeger, in *Atoms, molecules and clusters in electric fields: Theoretical approaches to the calculation of electric polarizability*, edited by G. Maroulis (Imperial College Press, 2006), chap. 1, pp. 1–32.

[8] A. S. Mayorov, D. C. Elias, M. Mucha-Kruczynski, R. V. Gorbachev, T. Tudorovskiy, A. Zhukov, S. V. Morozov, M. I. Katsnelson, V. I. Falko, A. K. Geim, et al., Science **333**, 860 (2011).